

## Capturing extracellular matrix properties in vitro: Microengineering materials to decipher cell and tissue level processes

Amr A Abdeen, Junmin Lee and Kristopher A Kilian

Department of Materials Science and Engineering, University of Illinois at Urbana-Champaign, Urbana, IL 61801, USA  
Corresponding author: Kristopher A. Kilian. Email: kakilian@illinois.edu

### Abstract

Rapid advances in biology have led to the establishment of new fields with tremendous translational potential including regenerative medicine and immunoengineering. One commonality to these fields is the need to extract cells for manipulation in vitro; however, results obtained in laboratory cell culture will often differ widely from observations made in vivo. To more closely emulate native cell biology in the laboratory, designer engineered environments have proved a successful methodology to decipher the properties of the extracellular matrix that govern cellular decision making. Here, we present an overview of matrix properties that affect cell behavior, strategies for recapitulating important parameters in vitro, and examples of how these properties can affect cell and tissue level processes, with emphasis on leveraging these tools for immunoengineering.

**Keywords:** Biomaterials, extracellular matrix, micropatterning

*Experimental Biology and Medicine* 2016; 241: 930–938. DOI: 10.1177/1535370216644532

### Introduction

Since the advent of in vitro cell culture in the early 20th century, epitomized by Harrison's development of the hanging drop technique to observe nerve fiber growth in 1907, it has provided a convenient, cost-effective method to study specific cell lines in minimal simplified growth conditions, free of many of the outside influences seen in vivo. This allows for isolation of single cell lines to investigate their properties, testing the effects of various pharmacological agents on specific cell types and a multitude of other applications under well-controlled conditions. However, these advantages come at a price; due to the differences between in vitro and in vivo cell culture conditions, cell characteristics change with long term in vitro culture. Cells adapt to the different culture conditions by changing their behavior and activities.<sup>1</sup>

With the accumulating evidence of the role that physical and mechanical factors such as forces,<sup>2</sup> shape,<sup>3</sup> and architecture<sup>4</sup> play in regulating cell behavior, the divide between in vitro cell culture and in vivo environments presents an obstacle to studying and manipulating cells in the laboratory. There have been several advances in materials and fabrication techniques that have allowed for modulation of the extracellular matrix (ECM) available to cells during in vitro culture. In fact, cells reside in very complex and dynamic extracellular matrices,<sup>5–8</sup> with very specific

compositions, ligand presentations, mechanical properties, and organization that vary between different tissues.<sup>9</sup> Extracellular factors strongly influence many facets of cell behavior such as homeostasis,<sup>10,11</sup> morphogenesis,<sup>12,13</sup> self-renewal and differentiation of stem cells,<sup>14</sup> development,<sup>6,15</sup> and disease.<sup>15,16</sup> It thus becomes clear that, in order to be able to more fully study cell behavior in vitro, cell culture platforms in which these factors can be recapitulated and/or manipulated must be developed.<sup>17</sup>

Although methods to confine cells to specific shapes have been demonstrated since 1967,<sup>18</sup> the more recent spread of lithographic,<sup>19</sup> microfluidic,<sup>20</sup> and other patterning techniques have made micropatterning of cells much more convenient and accessible. The increasing use of both natural and synthetic soft materials<sup>21–23</sup> have allowed for manipulation of the form and mechanical properties of the ECM as well as ligand presentation. ECM proteins and synthetic peptides enable more precise study of specific cell–ECM interactions.<sup>5</sup> Degradable<sup>24</sup> and dynamically tunable<sup>25</sup> platforms elucidate how cells react to changes in their microenvironments. Techniques such as 3D printing<sup>26</sup> and nanopatterning<sup>27</sup> allow for investigating processes on tissue and subcellular scales, respectively. These advances, along with others, have enabled engineered in vitro environments to be much more accurate model systems for in vivo processes, yielding considerable insights on cellular behavior.<sup>16,28</sup>

In this minireview, we explore engineered environments to study and control the effects of ECM properties on cell activity. For both single cell and multiple cell systems, we consider relevant ECM properties with examples of in vitro model systems that capture these properties, highlighting some insights gleaned from such systems. We then highlight some applications of microengineered materials for the emerging field of immuno-engineering.


## Engineered environments for single cell culture

Single cells experience a myriad of different signals from their ECM (Figure 1). Cells transduce and integrate these different factors into biochemical signals altering their behavior.<sup>29</sup> There are a variety of cellular apparatus used to detect extracellular signals such as growth factors and cytokine receptors, ion channels, cell-matrix, and cell-cell adhesion molecules.<sup>30</sup> Particularly, forces exerted by and on the cells through transmembrane receptors such as integrins play an important role through “mechanotransduction” via the cellular cytoskeleton.<sup>31–34</sup> Stem cells, with their plasticity, ability to differentiate down different

lineages, and importance for regenerative medicine, are particularly sensitive to extracellular cues and thus are the focus of several of these studies.<sup>35–37</sup>

## Matrix composition

Biochemical factors present in the extracellular space are numerous and present a multitude of signals to cells, allowing for functional complexity in cell behavior.<sup>44</sup> A wide variety of glycosaminoglycans (GAGs), proteoglycans, and different glycoproteins such as collagens, fibronectins (FNs), and laminins, combine together to provide a very rich signaling environment, which varies widely between different tissues. In fact, loss of function mutations in several of these proteins are embryonic lethal or post-natal lethal within four weeks,<sup>44</sup> highlighting their importance. However, due to the high complexity and organization, it is significantly challenging to recapitulate aspects of such an environment in vitro. A common strategy is adsorption<sup>45</sup> or chemical conjugation<sup>46</sup> of proteins onto synthetic tissue culture substrates. This method is more facile for studying the effects of single components of the ECM or simple combinations and is useful for deconstructing the roles of

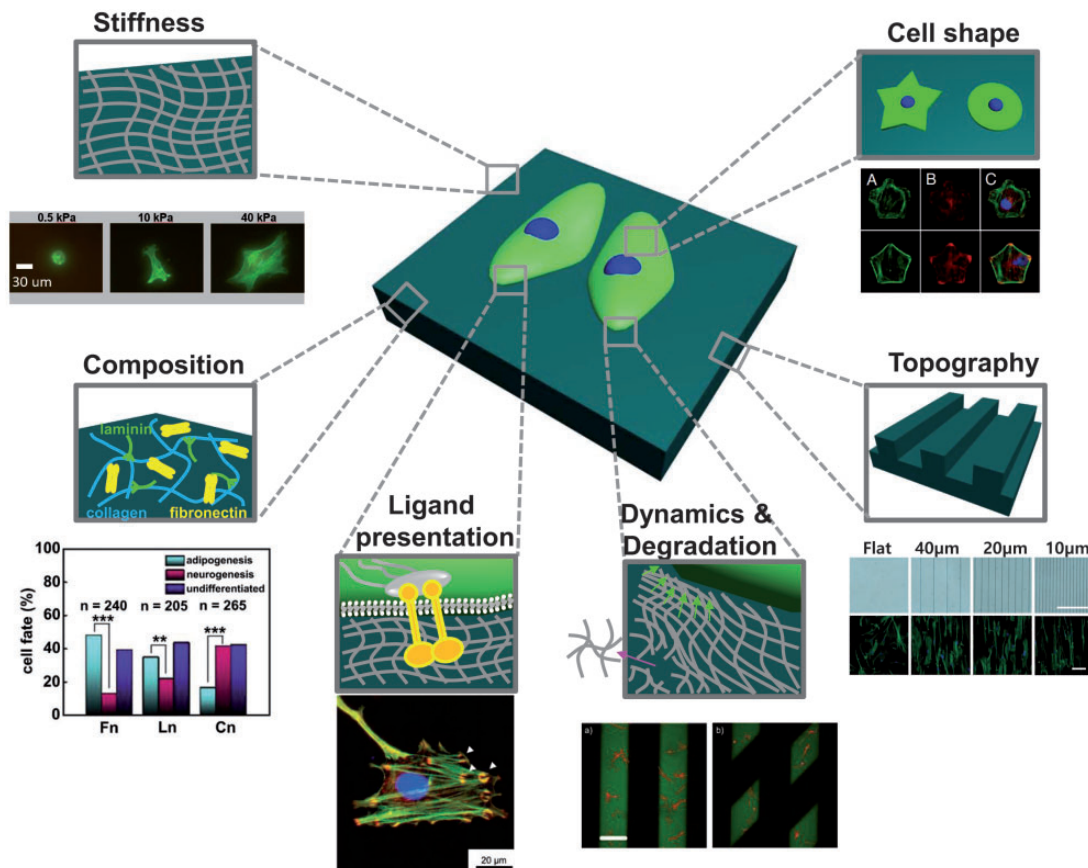

**Figure 1** Matrix properties affect cell behavior in vitro: *elasticity*—MSC morphology (and cytokine secretions) is dependent on matrix stiffness.<sup>38</sup> *Composition*—MSC differentiation is highly dependent on the matrix protein conjugated to the surface (reprinted by Lee et al.,<sup>39</sup> Copyright (2013), with permission from Elsevier). *Ligand presentation*—fibroblast focal adhesions only form on 5 μm RGD functionalized gold islands with stress fibers running between adhesions (reprinted with permission by Aydin et al.,<sup>40</sup> copyright (2010) American chemical society). *Dynamics and degradation*—cell adhesion can be switched on and off by switching the conjugation of ligands at the surface (reprinted by DeForest and Anseth,<sup>41</sup> Copyright (2012), with permission from Wiley). *Topography*—substrate topography controls alignment and epigenetic reprogramming of cells (reprinted by permission from Macmillan Publishers Ltd: Nature Materials by Downing et al.,<sup>42</sup> copyright (2013)). *Cell Shape*—modifying cell shape can affect MSC cytoskeleton, focal adhesion formation and differentiation.<sup>43</sup> (A color version of this figure is available in the online journal.)

different ECM components and their interactions. Both adsorption and chemical conjugation, however, may alter protein conformation, potentially changing protein bioactivity.<sup>47</sup> Other strategies include the use of natural ECM components, such as GAG or collagen gels, to fabricate tissue culture environments<sup>48</sup> or using decellularized matrices.<sup>49</sup> These strategies recapture several aspects of the *in vivo* environment but relinquish some control over the precise environment presented to cells. Matrix composition has been found to influence diverse aspects of cell behavior such as extracellular signal-regulated kinases (ERK) activation by mechanical strain in smooth muscle cells,<sup>50</sup> endothelial cells network formation and their response to transforming growth factor- $\beta$ ,<sup>51</sup> secretome,<sup>38</sup> cancer progression,<sup>52</sup> and stem cell fate.<sup>53</sup> We and other groups have shown previously that for mesenchymal stem cells (MSCs), matrix composition can direct cell differentiation and mediate how cells respond to other cues.<sup>39,54</sup> Two current areas of active research are the use of cell-derived matrices to reconstitute *in vitro* environments<sup>55</sup> and synthesis of matrices that can better interact with growth factors via sequestration and other interactions.<sup>56</sup>

### Ligand presentation

Cells will behave very differently depending on how the ligand presents to the cell. This mainly has to do with how cells interact with the proteins via focal adhesions, clusters of intracellular proteins, and transmembrane integrins.<sup>57,58</sup> These interactions physically transfer forces between the ECM and cells, facilitating mechanotransduction and cellular remodeling of the ECM.<sup>29,59</sup> Cell-matrix interactions are sensitive to ligand density, ligand spacing, receptor clustering, and ligand availability,<sup>60</sup> in addition to composition. Furthermore, the pliability of proteins to cell generated forces tunes the availability of cryptic signaling sites.<sup>30</sup> Several innovative methods have been developed to control these different aspects. The use of recombinant protein fragments or peptide sequences allows for tailoring of specific cell-matrix interactions since integrin pairs react with specific peptide sequences<sup>31</sup> with different affinities and outcomes. For example, using different FN III9-10 fragments with variable specificities to  $\alpha_5\beta_1$  integrins allows control of  $\alpha_5\beta_1$ -mediated MSC osteogenesis.<sup>61</sup> Self-assembled monolayers of alkanethiolates on gold substrates can be used to present a more uniform interface to cells and control ligand density and affinity.<sup>62,63</sup> Block copolymer micelle nanolithography,<sup>64</sup> a technique by which very uniform arrangements of gold nanodots can be made, has been used to study effects of ligand spacing and density variations and, when combined with micropatterning, the effects of ligand clustering. The use of such methods has revealed the different binding affinities of integrins depending on peptide sequences<sup>65</sup> (even depending on cyclic vs. linear variants of Arginylglycylaspartic acid (RGD),<sup>63</sup> a commonly used peptide sequence from FN) or adhesion clustering.<sup>66</sup> Moreover, Spatz et al.<sup>67</sup> have demonstrated a threshold of ~60 nm of ligand separation for activation of integrin function and more recently have reported a more dominant role for local ligand density as opposed to global.<sup>68</sup> Finally, density of protein tethering alters the

deformations exacted on proteins by cells, altering cell signaling, and MSC fate.<sup>69</sup>

### Cell shape

One of the challenges of *in vitro* cell culture is cell heterogeneity and poor replicability of results. Micropatterning of cell shape diminishes much of the heterogeneity inherent in cell culture substrates and controls for several aspects of cellular structure such as spread area and spatial distribution of adhesions,<sup>3</sup> allowing for better control over experiments. Furthermore, control over cell shape facilitates geometric manipulation of the structure of the cytoskeleton.<sup>3,70</sup> There are multiple methods of micropatterning cells including lithography,<sup>19</sup> photo-patterning,<sup>41</sup> microfluidics,<sup>71</sup> and microcontact printing.<sup>72</sup> Micropatterning does not have to be with integrin ligands but can utilize other cellular components such as lipid bilayers.<sup>73</sup> Cell shape can determine the structure of the cytoskeleton,<sup>70</sup> focal adhesions,<sup>74</sup> intermediate filaments,<sup>75</sup> internal cell organization,<sup>76</sup> nuclear forces,<sup>77</sup> and histone modifications.<sup>78,79</sup> Consequently, cell shape and size also influence cell viability,<sup>80</sup> stem cell multipotency,<sup>81</sup> and fate decisions.<sup>39,82</sup> Increasing the degree of cytoskeletal tension nudges MSCs toward an osteogenic, rather than adipogenic fate<sup>43</sup> and modulates integrin-mediated matrix interaction.<sup>83</sup>

### Elasticity

With the elasticity of various tissues spanning orders of magnitude,<sup>84</sup> ECM elasticity is one of the most studied physical factors influencing cell behavior. Mechanics have also been implicated in a wide array of pathologies.<sup>85,86</sup> Cells respond to changes in ECM elasticity,<sup>87</sup> often by changing their own properties as evidenced by fibroblasts matching stiffness to their substrates.<sup>88</sup> Biological materials are usually heterogeneous in mechanical properties and often display nonlinear elastic behavior.<sup>89</sup> Synthetic materials such as polymeric hydrogels and natural materials are routinely fabricated with tunable stiffness, and materials with variable rigidities such as micropost arrays<sup>90</sup> have been used to probe stiffness response as well. Various cytoskeletal components and signaling pathways have been implicated in these processes including focal adhesion kinase, Rho/Rock,<sup>35</sup> and Yes-associated protein (YAP)/transcriptional co-activator with PDZ-binding motif (TAZ)<sup>91</sup> as well as nuclear elements such as lamin-A<sup>92</sup> and Linker of Nucleoskeleton and Cytoskeleton (LINC) complexes.<sup>93</sup> Early studies showed that cell motion and focal adhesions are regulated by substrate elasticity.<sup>21</sup> Engler et al.<sup>94,95</sup> demonstrated that MSC fate depends on substrate compliance, with optimal differentiation marker expression occurring on elasticities matching *in vivo* elasticity. Since then, the influence of substrate elasticity on modulating several aspects of cell behavior has been well documented.<sup>96</sup> It has further been reported that the effects on MSCs depend on how long they are exposed to a substrate and that MSC behavior is affected by their mechanical history.<sup>97,98</sup> The mechanism, or what exactly the cells are responding to, is variable, since changing material stiffness typically entails changing material porosity, matrix tethering, and other mechanical properties. Response to mechanical



properties has been attributed to matrix elasticity,<sup>99,100</sup> density of protein tethering,<sup>69</sup> viscoelastic creep,<sup>101</sup> traction forces,<sup>102</sup> and stress relaxation.<sup>103</sup>

### Topography

As opposed to flat culture substrates, basement membranes, and ECM components such as collagen, which form submicron-sized fibrils, have a very hierarchical structure and are often textured, providing topographic signaling cues.<sup>104</sup> These cues, depending on their size, can interact with integrins up to whole cells. Advances in nanofabrication have allowed the formation of nanoscale gratings, posts, pits, aligned fibers, and other structures that can be made isotropic, anisotropic, or in gradient form.<sup>105,106</sup> Nanotopography can affect cell morphology, adhesion, migration, proliferation, and differentiation, generally through generation of anisotropic stresses in cells.<sup>106</sup> MSC differentiation has been reported to be guided by nanotopography, for example, to the neurogenic<sup>107</sup> or osteogenic<sup>108</sup> lineages. Recently, Downing et al.<sup>42</sup> have shown that microgrooves can modify the epigenetics and significantly improve the reprogramming of fibroblasts, demonstrating the large potential of topographic cues.

### Dynamic and degradable environments

The constantly changing nature of in vivo ECM is well known.<sup>52,109</sup> As stated above, cells react to changes in ECM properties but are affected by previous environments. For example, there have been recent reports that MSCs “remember” their previous substrates<sup>97,98</sup> for at least 10 days with regard to nuclear localization of RUNX2, YAP, and osteogenic differentiation, although other properties such as cell area remain plastic or relatively unaffected by previous states. This is a new field of study, however, and more work is required to understand the mechanisms through which cells maintain this memory and its effect on cell behavior for longer term. Dynamic materials are hence desirable to construe the effects of changing microenvironments on cells. Switchable surfaces,<sup>110</sup> stimuli responsive materials,<sup>111</sup> and photoresponsive materials<sup>41</sup> have been used to modulate matrix properties such as ligand presentation, composition, stiffness, and cell shape during cell culture. Furthermore, substrate degradability may be desirable for both probing cell behavior and for in vivo use of engineered substrates.<sup>24,112,113</sup> A significant challenge remains engineering reversibility into these kinds of systems as opposed to one-directional changes.<sup>114</sup>

Other factors such as dimensionality,<sup>23,115</sup> mechanical load, and shear flow are also potent regulators of cell behavior. Cell behavior is typically very different between 2D and 3D environments as evidenced by several studies.<sup>102,116,117</sup> Although it is extremely challenging to control for multiple aspects of ECM structure in the same experiment, it is important to evaluate data in context of all the appropriate properties of the system and how they relate to the relevant in vivo environments. Different components such as hydrogels and nanopatterning or micropatterning can be combined to study the effects of multiple factors concurrently.<sup>39,40</sup> In fact, studies combining multiple cues often


reveal crosstalk and interplay among different factors.<sup>59</sup> For example, MSC response to stiffness is dependent on matrix composition in terms of adhesion,<sup>83</sup> differentiation,<sup>39,54</sup> and therapeutic potential.<sup>38</sup> For this reason, it is imperative to take the whole biophysical system into consideration before making conclusions about the effects of certain parameters.

### Peer pressure: The influence of multicellular interactions

In addition to all the factors influencing single cells during culture, there are multiple additional effects in play when multicellular constructs are considered together (Figure 2). In this situation, the position of a cell relative to other cells, cell–cell interactions, paracrine signaling, and interactions with different cell types act to instruct cellular outcomes and coordinated cell behavior. This is particularly apparent during development where the relative positions of cells can dictate their specification and differentiation.<sup>6</sup> Although scaffolds for studying these kinds of behaviors are typically on a larger scale than those for single cells, great care must be taken to optimize the experimental parameters and define the specific interactions being studied in order to deconstruct specific cues and determine their precise influence. Here, we present a brief overview of some of these factors.

In a typical in vivo niche, there are multiple cell types in contact in different ways. Cells in contact interact through cadherins; a family of cell adhesion molecules which mediate interactions. Cadherin based cell–cell contacts are involved in a plethora of biological processes such as development, differentiation, and disease.<sup>118</sup> Multiple platforms have been developed wherein homo- and heterotypic cell–cell contacts can be controlled from a single cell–cell contact up to large scale co-cultures.<sup>119</sup> Cells in contact have been shown to mechanically couple together,<sup>120</sup> allowing for large scale collective cell migration.<sup>121</sup> Tseng et al.<sup>122</sup> have shown that the organization of intercellular junctions are dependent on the ECM architecture. Studying interactions of heterotypic cells has shown interesting phenomena such as natural cell sorting due to adhesion effects<sup>123</sup> and self-assembly of multicellular structures.<sup>124</sup> Artificial boundaries between different cell types allow the investigation of interfacial interactions (in tumor-stroma, for example).<sup>125</sup>

Cohesive forces between cells stabilize them in contact. Differences in adhesion between homophilic and heterophilic cell–cell contacts may cause cell aggregation and sorting,<sup>126</sup> analogous to surface tension in fluids.<sup>127</sup> The shapes of individual cells within aggregates depend on their position within the aggregate, which specifies their cortical tension and degree of cell–cell adhesion.<sup>128</sup> However, several other factors change at the surfaces of patterned cell aggregates, thereby complicating the interpretation of behavior. Some of these factors are mechanical stresses due to traction forces,<sup>129,130</sup> cytokine gradients caused by uneven distribution of cells,<sup>131</sup> and differences in surface curvature. Often, these factors feed into each other, giving an extra layer of complexity which can, however, be elucidated by usage of more controlled patterning methods such as the use of microfluidics to precisely control cytokine gradients.<sup>132</sup>

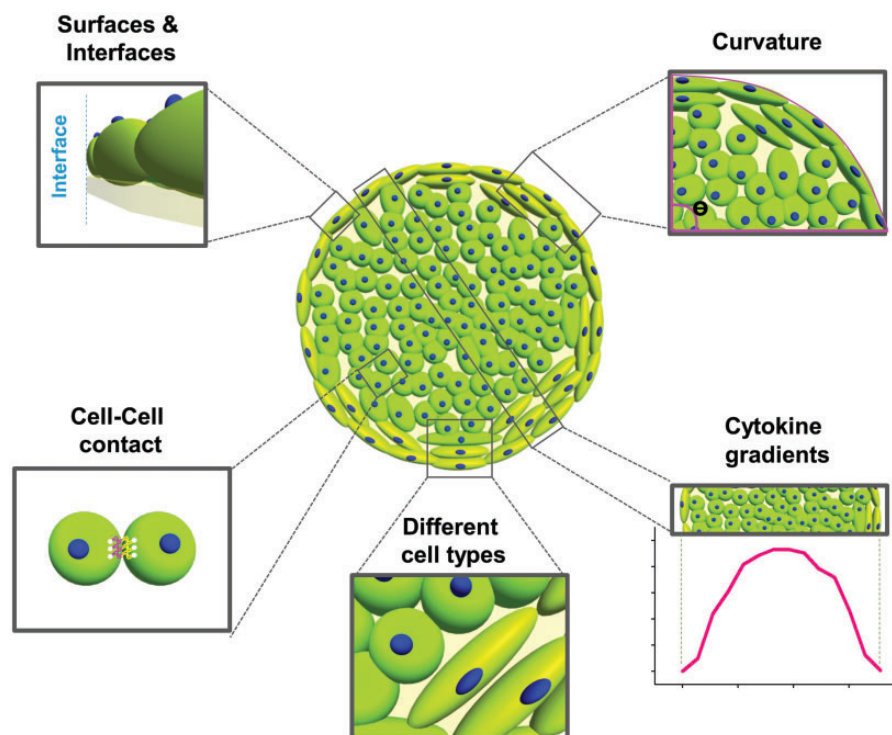

**Figure 2** Interactions of multiple cells. Several factors are introduced when multiple cells are considered together including cell-cell contact, contact between different cell types, the introduction of interfaces and curvature, and cytokine gradients across the system. These factors control effects such as collective cell behavior and cell sorting, for example. (A color version of this figure is available in the online journal.)

In addition to deconstructing the influences of different factors in the microenvironment, engineered matrices that can simultaneously control multiple cues may be used to optimize desired outcomes. For instance, 3D printing techniques have been developed that can control matrix composition, topography, elasticity, and spatial organization of different cell types which have been used to print vascularized, multiple cell-laden constructs.<sup>133</sup>

### Micropatterning techniques for immune engineering

With the complexity and various roles of the immune system, immune cells have evolved very sophisticated machinery to respond to different situations with suitable behavior. For example, macrophages have both pro-inflammatory and pro-healing, anti-inflammatory phenotypes with significant plasticity between them. These phenotypes are regulated according to both secreted factors and the physical environment, with dysregulation occurring in cancer and obesity, for example.<sup>134</sup> Understanding interactions of immune cells with biomaterials is crucial for understanding and controlling foreign body reactions for implants and is a major field of study.<sup>135</sup> Macrophage adhesion, activation, and fusion, contributing to fibrogenic reactions to foreign bodies, are dependent on culture environment,<sup>136,137</sup> such as stiffness<sup>138</sup> and cell shape<sup>139</sup> and may cause macrophages to remodel their ECM.<sup>140</sup> Furthermore, ECM effects have been studied in inflammation, wound healing, immunomodulation, and immune response to cancer.<sup>141,142</sup>

With the rise of immunoengineering, and the potential for controlling immune behavior across a host of processes, it is important to study, and make use of, the modulation of immune cells via ECM. There have been a few reports of the use of patterning strategies to modulate immune cells. Micropatterning of cell-cell junctions has been used to study cell interactions such as immunological synapses (IS), the junction between T lymphocytes (T-cells) and antigen presenting cells. Doh and Irvine<sup>143</sup> have shown, using micropatterning of T-cell receptors (TCR) and intercellular adhesion molecules in different structures, that T-cell assembly of ISs was strongly dependent on the unique physical structure of the synapse with stable interactions on focal spots of TCR ligands. More recent work by Tabdanov et al.<sup>144</sup> using similar methodology showed the effects of structure of ISs on the cytoskeletal mechanics of T-cells. Mossman et al.<sup>145</sup> have used nanopatterning techniques to constrain IS formation, elucidating a correlation between radial TCR position and signaling.<sup>145</sup> Adhesive protein micropatterns have been shown to affect fibrogenic activation of macrophages, with relevance to foreign body response.<sup>146</sup> Moreover, patterning of other cell components, such as lipid bilayers, can be used to further probe these systems.<sup>147</sup>

Single cell micropatterning has also been used with macrophages, white blood cells that perform phagocytosis. Patterning of cell shape was used by McWhorter et al.<sup>139</sup> to modulate the phenotype of macrophages between pro-inflammatory (M1) and pro-healing (M2) states by controlling elongation of single macrophages. Increase in cell

aspect ratio led to enhancement of M2-related cytokines and polarization through an actomyosin contractility dependent mechanism. More recently, micropatterning of macrophages was used to study the cytoskeletal effects of edema toxin<sup>148</sup> where reproducible control over the actin cytoskeleton was used to normalize cell response to toxin.

## Outlook

There are several reasons to implement physiologically relevant physical and chemical properties for in vitro scaffolds including the ability to study cells in a more complex “natural” environment, the development of more representative models to supplement or replace animal models, and the development of tissue engineering constructs which can be implanted and interfaced with existing tissue.<sup>17</sup> Studies using systems with tunable properties such as stiffness, composition, and cell shape will reveal dramatic changes in cell behavior compared to standard culture dishes, often with the recurring theme of large changes at physiologically relevant matrix properties. However, studies with multiple cues often reflect a coupling between these different factors, complicating the establishment of parameter-function relationships. Going forward, developing platforms that can capture the complexity of the native ECM while also having the ability to quantitatively, precisely, and specifically tune matrix properties to deconstruct and control the effects of various cues, are crucial for in vitro study of cells, development of model systems and development of scaffolds for tissue engineering and regenerative medicine applications.

**Author contributions:** All authors participated in the writing and review of the manuscript.

## ACKNOWLEDGMENTS

The Kilian laboratory is supported by funding from the National Science Foundation Grant # 1454616 CAR and the National Heart Lung and Blood Institute of the National Institutes of Health, grant number HL121757.

## DECLARATION OF CONFLICTING INTERESTS

The author(s) declared no potential conflicts of interest with respect to the research, authorship, and/or publication of this article.

## REFERENCES

- Hughes P, Marshall D, Reid Y, Parkes H, Gelber C. The costs of using unauthenticated, over-passaged cell lines: How much more data do we need? *Biotechniques* 2007;**43**:575–86
- Soediono B. *Mechanical forces: their effects on cells and tissues*. Berlin: Springer Berlin Heidelberg, 1997
- Théry M. Micropatterning as a tool to decipher cell morphogenesis and functions. *J Cell Sci* 2010;**123**:4201–13
- DuFort CC, Paszek MJ, Weaver VM. Balancing forces: architectural control of mechanotransduction. *Nat Rev Mol Cell Biol* 2011;**12**:308–19
- Frantz C, Stewart KM, Weaver VM. The extracellular matrix at a glance. *J Cell Sci* 2010;**123**:4195–200
- Daley WP, Peters SB, Larsen M. Extracellular matrix dynamics in development and regenerative medicine. *J Cell Sci* 2008;**121**:255–64
- Mouw JK, Ou G, Weaver VM. Extracellular matrix assembly: a multi-scale deconstruction. *Nat Rev Mol Cell Biol* 2014;**15**:771–85
- Nelson CM, Bissell MJ. Of extracellular matrix, scaffolds, and signaling: tissue architecture regulates development, homeostasis, and cancer. *Annu Rev Cell Dev Biol* 2006;**22**:287–309
- Adams JC, Watt FM. Regulation of development and differentiation by the extracellular matrix. *Development* 1993;**117**:1183–98
- Humphrey JD, Dufresne ER, Schwartz MA. Mechanotransduction and extracellular matrix homeostasis. *Nat Rev Mol Cell Biol* 2014;**15**:802–12
- Kolahi KS, Mofrad MRK. Mechanotransduction: a major regulator of homeostasis and development. *Wiley Interdiscip Rev Syst Biol Med* 2010;**2**:625–39
- Kim HY, Nelson CM. Extracellular matrix and cytoskeletal dynamics during branching morphogenesis. *Organogenesis* 2012;**8**:56–64
- Heisenberg C-P, Bellaïche Y. Forces in tissue morphogenesis and patterning. *Cell* 2013;**153**:948–62
- Wang JH-C, Thampatty BP. Mechanobiology of adult and stem cells. *Int Rev Cell Mol Biol* 2008;**271**:301–46
- Bonnans C, Chou J, Werb Z. Remodelling the extracellular matrix in development and disease. *Nat Rev Mol Cell Biol* 2014;**15**:786–801
- Lukashev ME, Werb Z. ECM signalling: orchestrating cell behaviour and misbehaviour. *Trends Cell Biol* 1998;**8**:437–41
- Griffith LG, Swartz MA. Capturing complex 3D tissue physiology in vitro. *Nat Rev Mol Cell Biol* 2006;**7**:211–24
- Carter SB. Haptotactic islands: a method of confining single cells to study individual cell reactions and clone formation. *Exp Cell Res* 1967;**48**:189–93
- Kane RS, Takayama S, Ostuni E, Ingber DE, Whitesides GM. Patterning proteins and cells using soft lithography. *Biomaterials* 1999;**20**:2363–76
- Velve-Casquillas G, Le Berre M, Piel M, Tran PT. Microfluidic tools for cell biological research. *Nano Today* 2010;**5**:28–47
- Pelham R, Wang Y. Cell locomotion and focal adhesions are regulated by substrate flexibility. *Proc Natl Acad Sci U S A* 1997;**94**:13661–5
- Dhandayuthapani B, Yoshida Y, Maekawa T, Kumar DS. Polymeric scaffolds in tissue engineering application: a review. *Int J Polym Sci* 2011;**2011**:1–19
- Tibbitt MW, Anseth KS. Hydrogels as extracellular matrix mimics for 3D cell culture. *Biotechnol Bioeng* 2009;**103**:655–63
- Kharkar PM, Kiick KL, Kloxin AM. Designing degradable hydrogels for orthogonal control of cell microenvironments. *Chem Soc Rev* 2013;**42**:7335–72
- Eliyahu-Gross S, Bitton R. Environmentally responsive hydrogels with dynamically tunable properties as extracellular matrix mimetic. *Rev Chem Eng* 2013;**29**:1–10
- Murphy SV, Atala A. 3D bioprinting of tissues and organs. *Nat Biotechnol* 2014;**32**:773–85
- Singh AV, Patil R, Thombre DK, Gade WN. Micro-nanopatterning as tool to study the role of physicochemical properties on cell-surface interactions. *J Biomed Mater Res A* 2013;**101**:3019–32
- Rosso F, Giordano A, Barbarisi M, Barbarisi A. From cell-ECM interactions to tissue engineering. *J Cell Physiol* 2004;**199**:174–80
- Kim SH, Turnbull J, Guimond S. Extracellular matrix and cell signalling: the dynamic cooperation of integrin, proteoglycan and growth factor receptor. *J Endocrinol* 2011;**209**:139–51
- Vogel V, Sheetz M. Local force and geometry sensing regulate cell functions. *Nat Rev Mol Cell Biol* 2006;**7**:265–75
- Campbell ID, Humphries MJ. Integrin structure, activation, and interactions. *Cold Spring Harb Perspect Biol* 2011;**3**:a004994
- Schwartz MA. Integrins and extracellular matrix in mechanotransduction. *Cold Spring Harb Perspect Biol* 2010;**2**:a005066
- Schwarz US, Gardel ML. United we stand: integrating the actin cytoskeleton and cell-matrix adhesions in cellular mechanotransduction. *J Cell Sci* 2012;**125**:3051–60
- Paluch EK, Nelson CM, Biais N, Fabry B, Moeller J, Pruitt BL, Wollnik C, Kudryasheva G, Rehfeldt F, Federle W. Mechanotransduction: use the force(s). *BMC Biol* 2015;**13**:47
- Sun Y, Chen CS, Fu J. Forcing stem cells to behave: a biophysical perspective of the cellular microenvironment. *Annu Rev Biophys* 2012;**41**:519–42



36. Lutolf MP, Gilbert PM, Blau HM. Designing materials to direct stem-cell fate. *Nature* 2009;**462**:433–41
37. Lee DA, Knight MM, Campbell JJ, Bader DL. Stem cell mechanobiology. *J Cell Biochem* 2011;**112**:1–9
38. Abdeen AA, Weiss JB, Lee J, Kilian KA. Matrix composition and mechanics direct proangiogenic signaling from mesenchymal stem cells. *Tissue Eng Part A* 2014;**20**:2737–45
39. Lee J, Abdeen AA, Zhang D, Kilian KA. Directing stem cell fate on hydrogel substrates by controlling cell geometry, matrix mechanics and adhesion ligand composition. *Biomaterials* 2013;**34**:8140–8
40. Aydin D, Louban I, Perschmann N, Blümmel J, Lohmüller T, Cavalcanti-Adam EA, Haas TL, Walczak H, Kessler H, Fiammengio R, Spatz JP. Polymeric substrates with tunable elasticity and nanoscopically controlled biomolecule presentation. *Langmuir* 2010;**26**:15472–80
41. DeForest CA, Anseth KS. Photoreversible patterning of biomolecules within click-based hydrogels. *Angew Chem Int Ed Engl* 2012;**51**:1816–9
42. Downing TL, Soto J, Morez C, Houssin T, Fritz A, Yuan F, Chu J, Patel S, Schaffer DV, Li S. Biophysical regulation of epigenetic state and cell reprogramming. *Nat Mater* 2013;**12**:1154–62
43. Kilian KA, Bugarija B, Lahn BT, Mrksich M. Geometric cues for directing the differentiation of mesenchymal stem cells. *Proc Natl Acad Sci U S A* 2010;**107**:4872–7
44. Rozario T, DeSimone DW. The extracellular matrix in development and morphogenesis: a dynamic view. *Dev Biol* 2010;**341**:126–40
45. Wilson CJ, Clegg RE, Leavesley DI, Pearcy MJ. Mediation of biomaterial–cell interactions by adsorbed proteins: a review. *Tissue Eng* 2005;**11**:1–18
46. Hermanson GT. Bioconjugation in the study of protein interactions. In: Hermanson GT (ed.). *Bioconjugate techniques*. Amsterdam: Elsevier, 2013, pp. 989–1016
47. Thevenot P, Hu W, Tang L. Surface chemistry influences implant biocompatibility. *Curr Top Med Chem* 2008;**8**:270–80
48. Mano JF, Silva GA, Azevedo HS, Malafaya PB, Sousa RA, Silva SS, Boesel LF, Oliveira JM, Santos TC, Marques AP, Neves NM, Reis RL. Natural origin biodegradable systems in tissue engineering and regenerative medicine: present status and some moving trends. *J R Soc Interface* 2007;**4**:999–1030
49. Crapo PM, Gilbert TW, Badylak SF. An overview of tissue and whole organ decellularization processes. *Biomaterials* 2011;**32**:3233–43
50. Reusch HP, Chan G, Ives HE, Nemenoff RA. Activation of JNK/SAPK and ERK by mechanical strain in vascular smooth muscle cells depends on extracellular matrix composition. *Biochem Biophys Res Commun* 1997;**237**:239–44
51. Madri JA, Pratt BM, Tucker AM. Phenotypic modulation of endothelial cells by transforming growth factor-beta depends upon the composition and organization of the extracellular matrix. *J Cell Biol* 1988;**106**:1375–84
52. Lu P, Weaver VM, Werb Z. The extracellular matrix: a dynamic niche in cancer progression. *J Cell Biol* 2012;**196**:395–406
53. Watt FM, Huck WTS. Role of the extracellular matrix in regulating stem cell fate. *Nat Rev Mol Cell Biol* 2013;**14**:467–73
54. Rowlands AS, George PA, Cooper-White JJ. Directing osteogenic and myogenic differentiation of MSCs: interplay of stiffness and adhesive ligand presentation. *Am J Physiol Cell Physiol* 2008;**295**:1037–44
55. Fitzpatrick LE, McDevitt TC. Cell-derived matrices for tissue engineering and regenerative medicine applications. *Biomater Sci* 2015;**3**:12–24
56. Hudalla GA, Murphy WL. Biomaterials that regulate growth factor activity via bioinspired interactions. *Adv Funct Mater* 2011;**21**:1754–68
57. Geiger B, Spatz JP, Bershadsky AD. Environmental sensing through focal adhesions. *Nat Rev Mol Cell Biol* 2009;**10**:21–33
58. Cavalcanti-Adam EA, Aydin D, Hirschfeld-Warneken VC, Spatz JP. Cell adhesion and response to synthetic nanopatterned environments by steering receptor clustering and spatial location. *HFSP J* 2008;**2**:276–85
59. Minton K. Cell adhesion: integrating the integrin response. *Nat Rev Mol Cell Biol* 2013;**14**:3605
60. Satav T, Huskens J, Jonkheijm P. Effects of variations in ligand density on cell signaling. *Small* 2015;**11**:5184–99
61. Martino MM, Mochizuki M, Rothenfluh DA, Rempel SA, Hubbell JA, Barker TH. Controlling integrin specificity and stem cell differentiation in 2D and 3D environments through regulation of fibronectin domain stability. *Biomaterials* 2009;**30**:1089–97
62. Mrksich M. Using self-assembled monolayers to model the extracellular matrix. *Acta Biomater* 2010;**5**:832–41
63. Kilian KA, Mrksich M. Directing stem cell fate by controlling the affinity and density of ligand-receptor interactions at the biomaterials interface. *Angew Chem Int Ed Engl* 2012;**51**:4891–5
64. Lohmüller T, Aydin D, Schwieder M, Morhard C, Louban I, Pacholski C, Spatz JP. Nanopatterning by block copolymer micelle nanolithography and bioinspired applications. *Biointerphases* 2011;**6**:MR1–12
65. Roca-Cusachs P, Iskratsch T, Sheetz MP. Finding the weakest link: exploring integrin-mediated mechanical molecular pathways. *J Cell Sci* 2012;**125**:3025–38
66. Roca-Cusachs P, del Rio A, Puklin-Faucher E, Gauthier NC, Biais N, Sheetz MP. Integrin-dependent force transmission to the extracellular matrix by alpha-actinin triggers adhesion maturation. *Proc Natl Acad Sci U S A* 2013;**110**:E1361–70
67. Arnold M, Cavalcanti-Adam EA, Glass R, Blümmel J, Eck W, Kantelehner M, Kessler H, Spatz JP. Activation of integrin function by nanopatterned adhesive interfaces. *ChemPhysChem* 2004;**5**:383–8
68. Deeg JA, Louban I, Aydin D, Selhuber-Unkel C, Kessler H, Spatz JP. Impact of local versus global ligand density on cellular adhesion. *Nano Lett* 2011;**11**:1469–76
69. Trappmann B, Gautrot JE, Connelly JT, Strange DGT, Li Y, Oyen ML, Cohen Stuart M, Boehm H, Li B, Vogel V, Spatz JP, Watt FM, Huck WTS. Extracellular-matrix tethering regulates stem-cell fate. *Nat Mater* 2012;**11**:642–9
70. Théry M, Pépin A, Dressaire E, Chen Y, Bornens M. Cell distribution of stress fibres in response to the geometry of the adhesive environment. *Cell Motil Cytoskeleton* 2006;**63**:341–55
71. Tumarkin E, Tzadu L, Csaszar E, Seo M, Zhang H, Lee A, Peerani R, Purpura K, Zandstra PW, Kumacheva E. High-throughput combinatorial cell co-culture using microfluidics. *Integr Biol (Camb)* 2011;**3**:653–62
72. Alom Ruiz S, Chen CS. Microcontact printing: a tool to pattern. *Soft Matter* 2007;**3**:168
73. Hughes LD, Boxer SG. DNA-based patterning of tethered membrane patches. *Langmuir* 2013;**29**:12220–7
74. Chien F-C, Kuo CW, Yang Z-H, Chueh D-Y, Chen P. Exploring the formation of focal adhesions on patterned surfaces using super-resolution imaging. *Small* 2011;**7**:2906–13
75. Shabbir SH, Cleland MM, Goldman RD, Mrksich M. Geometric control of vimentin intermediate filaments. *Biomaterials* 2014;**35**:1359–66
76. Théry M, Racine V, Piel M, Pépin A, Dimitrov A, Chen Y, Sibarita J-B, Bornens M. Anisotropy of cell adhesive microenvironment governs cell internal organization and orientation of polarity. *Proc Natl Acad Sci U S A* 2006;**103**:19771–6
77. Versaevael M, Grevesse T, Gabriele S. Spatial coordination between cell and nuclear shape within micropatterned endothelial cells. *Nat Commun* 2012;**3**:671
78. Jain N, Iyer KV, Kumar A, Shivashankar GV. Cell geometric constraints induce modular gene-expression patterns via redistribution of HDAC3 regulated by actomyosin contractility. *Proc Natl Acad Sci U S A* 2013;**110**:3–8
79. Le Beyec J, Xu R, Lee S-Y, Nelson CM, Rizki A, Alcaraz J, Bissell MJ. Cell shape regulates global histone acetylation in human mammary epithelial cells. *Exp Cell Res* 2007;**313**:3066–75
80. Chen CS, Mrksich M, Huang S, Whitesides GM, Ingber DE. Geometric control of cell life and death. *Science* 1997;**276**:1425–8
81. Zhang D, Kilian KA. The effect of mesenchymal stem cell shape on the maintenance of multipotency. *Biomaterials* 2013;**34**:3962–9
82. McBeath R, Pirone DM, Nelson CM, Bhadriraju K, Chen CS. Cell shape, cytoskeletal tension, and RhoA regulate stem cell lineage commitment. *Dev Cell* 2004;**6**:483–95
83. Lee J, Abdeen AA, Tang X, Saif TA, Kilian KA. Geometric guidance of integrin mediated traction stress during stem cell differentiation. *Biomaterials* 2015;**69**:174–83
84. Akhtar R, Sherratt MJ, Cruickshank JK, Derby B. Characterizing the elastic properties of tissues. *Mater Today* 2011;**14**:96–105

85. Jaalouk DE, Lammerding J. Mechanotransduction gone awry. *Nat Rev Mol Cell Biol* 2009;**10**:63–73
86. Takahashi K, Kakimoto Y, Toda K, Naruse K. Mechanobiology in cardiac physiology and diseases. *J Cell Mol Med* 2013;**17**:225–32
87. Discher DE, Janmey P, Wang Y-L. Tissue cells feel and respond to the stiffness of their substrate. *Science* 2005;**310**:1139–43
88. Solon J, Levental I, Sengupta K, Georges PC, Janmey PA. Fibroblast adaptation and stiffness matching to soft elastic substrates. *Biophys J* 2007;**93**:4453–61
89. Storm C, Pastore JJ, MacKintosh FC, Lubensky TC, Janmey PA. Nonlinear elasticity in biological gels. *Nature* 2005;**435**:191–4
90. Han SJ, Bielawski KS, Ting LH, Rodriguez ML, Sniadecki NJ. Decoupling substrate stiffness, spread area, and micropost density: a close spatial relationship between traction forces and focal adhesions. *Biophys J* 2012;**103**:640–8
91. Dupont S, Morsut L, Aragona M, Enzo E, Giulitti S, Cordenonsi M, Zanconato F, Le Digabel J, Forcato M, Bicciato S, Elvassore N, Piccolo S. Role of YAP/TAZ in mechanotransduction. *Nature* 2011;**474**:179–83
92. Swift J, Ivanovska IL, Buxboim A, Harada T, Dingal PCDP, Pinter J, Pajeroski JD, Spinler KR, Shin J-W, Tewari M, Rehfeldt F, Speicher DW, Discher DE. Nuclear lamin-A scales with tissue stiffness and enhances matrix-directed differentiation. *Science* 2013;**341**:1240104
93. Wang N, Tytell JD, Ingber DE. Mechanotransduction at a distance: mechanically coupling the extracellular matrix with the nucleus. *Nat Rev Mol Cell Biol* 2009;**10**:75–82
94. Engler AJ, Sen S, Sweeney HL, Discher DE. Matrix elasticity directs stem cell lineage specification. *Cell* 2006;**126**:677–89
95. Engler AJ, Griffin MA, Sen S, Bönnemann CG, Sweeney HL, Discher DE. Myotubes differentiate optimally on substrates with tissue-like stiffness: pathological implications for soft or stiff micro-environments. *J Cell Biol* 2004;**166**:877–87
96. Han F, Zhu C, Guo Q, Yang H, Li B. Cellular modulation by the elasticity of biomaterials. *J Mater Chem B* 2016;**4**:9–26
97. Yang C, Tibbitt MW, Basta L, Anseth KS. Mechanical memory and dosing influence stem cell fate. *Nat Mater* 2014;**13**:645–52
98. Lee J, Abdeen AA, Kilian KA. Rewiring mesenchymal stem cell lineage specification by switching the biophysical microenvironment. *Sci Rep* 2014;**4**:5188
99. Wen JH, Vincent LG, Fuhrmann A, Choi YS, Hribar KC, Taylor-Weiner H, Chen S, Engler AJ. Interplay of matrix stiffness and protein tethering in stem cell differentiation. *Nat Mater* 2014;**13**:979–87
100. Huebsch N, Lippens E, Lee K, Mehta M, Koshy ST, Darnell MC, Desai R, Madl CM, Xu M, Zhao X, Chaudhuri O, Verbeke C, Kim WS, Alim K. Matrix elasticity of void-forming hydrogels controls matrix elasticity of void-forming hydrogels controls transplanted stem cell-mediated bone. *Nat Mater* 2015;**14**:1–19
101. Cameron AR, Frith JE, Cooper-White JJ. The influence of substrate creep on mesenchymal stem cell behaviour and phenotype. *Biomaterials* 2011;**32**:5979–93
102. Khetan S, Guvendiren M, Legant WR, Cohen DM, Chen CS, Burdick JA. Degradation-mediated cellular traction directs stem cell fate in covalently crosslinked three-dimensional hydrogels. *Nat Mater* 2013;**12**:458–65
103. Chaudhuri O, Gu L, Klumpers D, Darnell M, Bencherif SA, Weaver JC, Huebsch N, Lee H, Lippens E, Duda GN, Mooney DJ. Hydrogels with tunable stress relaxation regulate stem cell fate and activity. *Nat Mater* 2015;**15**:326–34
104. Kim D-H, Provenzano PP, Smith CL, Levchenko A. Matrix nanotopography as a regulator of cell function. *J Cell Biol* 2012;**197**:351–60
105. Norman JJ, Desai TA. Methods for fabrication of nanoscale topography for tissue engineering scaffolds. *Ann Biomed Eng* 2006;**34**:89–101
106. Bettinger CJ, Langer R, Borenstein JT. Engineering substrate topography at the micro- and nanoscale to control cell function. *Angew Chemie Int Ed* 2009;**48**:5406–15
107. Yim EKF, Pang SW, Leong KW. Synthetic nanostructures inducing differentiation of human mesenchymal stem cells into neuronal lineage. *Exp Cell Res* 2007;**313**:1820–9
108. Dalby MJ, Gadegaard N, Tare R, Andar A, Riehle MO, Herzyk P, Wilkinson CDW, Oreffo ROC. The control of human mesenchymal cell differentiation using nanoscale symmetry and disorder. *Nat Mater* 2007;**6**:997–1003
109. Cox TR, Erler JT. Remodeling and homeostasis of the extracellular matrix: implications for fibrotic diseases and cancer. *Dis Model Mech* 2011;**4**:165–78
110. Banik BL, Brown JL. 8—interaction of responsive/switchable surfaces with cells. In: Zhang Z (ed.). *Switchable and responsive surfaces and materials for biomedical applications*. Oxford: Woodhead Publishing, 2015, pp. 45–64
111. Kim J, Hayward RC. Mimicking dynamic in vivo environments with stimuli-responsive materials for cell culture. *Trends Biotechnol* 2012;**30**:426–39
112. Raeber GP, Lutolf MP, Hubbell JA. Molecularly engineered PEG hydrogels: a novel model system for proteolytically mediated cell migration. *Biophys J* 2005;**89**:1374–88
113. Kloxin AM, Kloxin CJ, Bowman CN, Anseth KS. Mechanical properties of cellularly responsive hydrogels and their experimental determination. *Adv Mater* 2010;**22**:3484–94
114. Burdick JA, Murphy WL. Moving from static to dynamic complexity in hydrogel design. *Nat Commun* 2012;**3**:1269
115. Baker BM, Chen CS. Deconstructing the third dimension: how 3D culture microenvironments alter cellular cues. *J Cell Sci* 2012;**125**:3015–24
116. Fischbach C, Kong HJ, Hsiong SX, Evangelista MB, Yuen W, Mooney DJ. Cancer cell angiogenic capability is regulated by 3D culture and integrin engagement. *Proc Natl Acad Sci U S A* 2009;**106**:399–404
117. DeVolder R, Kong H-J. Hydrogels for in vivo-like three-dimensional cellular studies. *Wiley Interdiscip Rev Syst Biol Med* 2012;**4**:351–65
118. Leckband D, Prakasam A. Mechanism and dynamics of cadherin adhesion. *Annu Rev Biomed Eng* 2006;**8**:259–87
119. Goubko CA, Cao X. Patterning multiple cell types in co-cultures: a review. *Mater Sci Eng C* 2009;**29**:1855–68
120. Huang S, Brangwynne CP, Parker KK, Ingber DE. Symmetry-breaking in mammalian cell cohort migration during tissue pattern formation: Role of random-walk persistence. *Cell Motil Cytoskeleton* 2005;**61**:201–13
121. Petitjean L, Reffay M, Grasland-Mongrain E, Poujade M, Ladoux B, Buguin A, Silberzan P. Velocity fields in a collectively migrating epithelium. *Biophys J* 2010;**98**:1790–800
122. Tseng Q, Duchemin-Pelletier E, Deshiere A, Balland M, Guillou H, Filhol O, Thery M. Spatial organization of the extracellular matrix regulates cell-cell junction positioning. *Proc Natl Acad Sci U S A* 2012;**109**:1506–11
123. Lecuit T, Lenne P-F. Cell surface mechanics and the control of cell shape, tissue patterns and morphogenesis. *Nat Rev Mol Cell Biol* 2007;**8**:633–44
124. Jakab K, Norotte C, Marga F, Murphy K, Vunjak-Novakovic G, Forgacs G. Tissue engineering by self-assembly and bio-printing of living cells. *Biofabrication* 2010;**2**:022001
125. Shen K, Luk S, Hicks DF, Elman JS, Bohr S, Iwamoto Y, Murray R, Pena K, Wang F, Seker E, Weissleder R, Yarmush ML, Toner M, Sgroi D, Parekkadan B. Resolving cancer–stroma interfacial signalling and interventions with micropatterned tumour–stromal assays. *Nat Commun* 2014;**5**:5662
126. Foty RA, Steinberg MS. Differential adhesion in model systems. *Wiley Interdiscip Rev Dev Biol* 2013;**2**:631–45
127. Beysens DA, Forgacs G, Glazier JA. Cell sorting is analogous to phase ordering in fluids. *Proc Natl Acad Sci U S A* 2000;**97**:9467–71
128. Manning ML, Foty RA, Steinberg MS, Schoetz E-M. Coaction of intercellular adhesion and cortical tension specifies tissue surface tension. *Proc Natl Acad Sci U S A* 2010;**107**:12517–22
129. Nelson CM, Jean RP, Tan JL, Liu WF, Sniadecki NJ, Spector AA, Chen CS. Emergent patterns of growth controlled by multicellular form and mechanics. *Proc Natl Acad Sci U S A* 2005;**102**:11594–9



130. Gomez EW, Chen QK, Gjorevski N, Nelson CM. Tissue geometry patterns epithelial-mesenchymal transition via intercellular mechanotransduction. *J Cell Biochem* 2010;**110**:44–51
131. Nelson CM, Vanduijn MM, Inman JL, Fletcher DA, Bissell MJ. Tissue geometry determines sites of mammary branching morphogenesis in organotypic cultures. *Science* 2006;**314**:298–300
132. Keenan TM, Folch A. Biomolecular gradients in cell culture systems. *Lab Chip* 2008;**8**:34–57
133. Kolesky DB, Truby RL, Gladman AS, Busbee TA, Homan KA, Lewis JA. 3D bioprinting of vascularized, heterogeneous cell-laden tissue constructs. *Adv Mater* 2014;**26**:3124–30
134. Mosser DM, Edwards JP. Exploring the full spectrum of macrophage activation. *Nat Rev Immunol* 2008;**8**:958–69
135. Franz S, Rammelt S, Scharnweber D, Simon JC. Immune responses to implants—a review of the implications for the design of immunomodulatory biomaterials. *Biomaterials* 2011;**32**:6692–709
136. Sridharan R, Cameron AR, Kelly DJ, Kearney CJ, O'Brien FJ. Biomaterial based modulation of macrophage polarization: a review and suggested design principles. *Mater Today* 2015;**18**:313–25
137. de Fougères AR, Kotliansky VE. Regulation of monocyte gene expression by the extracellular matrix and its functional implications. *Immunol Rev* 2002;**186**:208–20
138. Blakney AK, Swartzlander MD, Bryant SJ. The effects of substrate stiffness on the in vitro activation of macrophages and in vivo host response to poly(ethyleneglycol)-based hydrogels. *J Biomed Mater Res A* 2012;**100A**:1375–86
139. McWhorter FY, Wang T, Nguyen P, Chung T, Liu WF. Modulation of macrophage phenotype by cell shape. *Proc Natl Acad Sci U S A* 2013;**110**:17253–8
140. Anderson JM, Rodriguez A, Chang DT. Foreign body reaction to biomaterials. *Semin Immunol* 2008;**20**:86–100
141. Sorokin L. The impact of the extracellular matrix on inflammation. *Nat Rev Immunol* 2010;**10**:712–23
142. Vinet L, Zhedanov A. *Biomaterials in regenerative medicine and the immune system*. Cham: Springer International Publishing, 2015
143. Doh J, Irvine DJ. Immunological synapse arrays: patterned protein surfaces that modulate immunological synapse structure formation in T cells. *Proc Natl Acad Sci U S A* 2006;**103**:5700–5
144. Tabdanov E, Gondarenko S, Kumari S, Liapis A, Dustin ML, Sheetz MP, Kam LC, Iskratsch T. Micropatterning of TCR and LFA-1 ligands reveals complementary effects on cytoskeleton mechanics in T cells. *Integr Biol* 2015;**7**:1272–84
145. Mossman KD, Campi G, Groves JT, Dustin ML. Altered TCR signaling from geometrically repatterned immunological synapses. *Science* 2005;**310**:1191–3
146. Majd H, Scherer SS, Boo S, Ramondetti S, Cambridge E, Raffoul W, Friedrich M, Pittet B, Pioletti D, Hinz B, Pietramaggiore G. Novel micropatterns mechanically control fibrotic reactions at the surface of silicone implants. *Biomaterials* 2015;**54**:136–47
147. Groves JT, Dustin ML. Supported planar bilayers in studies on immune cell adhesion and communication. *J Immunol Methods* 2003;**278**:19–32
148. Trescos Y, Tessier E, Rougeaux C, Goossens PL, Tournier J-N. Micropatterned macrophage analysis reveals global cytoskeleton constraints induced by *Bacillus anthracis* edema toxin. *Infect Immun* 2015;**83**:3114–25